

Luminescence of a Cooper Pair

Yasuhiro Asano¹, Ikuo Suemune^{2,3}, Hideaki Takayanagi^{3,4,5}, and Eiichi Hanamura⁶

¹*Department of Applied Physics, Hokkaido University, Sapporo 060-8628, Japan.*

²*Research Institute for Electronic Science, Hokkaido University, Sapporo 001-0021, Japan.*

³*CREST, Japan Science and Technology Agency, Kawaguchi 332-0012, Japan.*

⁴*Department of Applied Physics, Tokyo University of Science, Tokyo 162-8601, Japan.*

⁵*International Center for Nanoarchitectonics, NIMS, Tsukuba 305-0044, Japan.*

⁶*Japan Science and Technology Agency, Kawaguchi 332-0012, Japan.*

(Dated: May 8, 2009)

This paper theoretically discusses the photon emission spectra of a superconducting pn-junction. On the basis of the second order perturbation theory for electron-photon interaction, we show that the recombination of a Cooper with two p-type carriers causes drastic enhancement of the luminescence intensity. The calculated results of photon emission spectra explain characteristic features of observed signal in an recent experiment. Our results indicate high functionalities of superconducting light-emitting devices.

PACS numbers: 74.50.+r, 74.25.Fy, 74.70.Tx

Light-emitting diode (LED) usually fabricated on semiconductors has been an important element of modern technologies. A trend of research seems to be focusing on producing a better controlled photon and an entangled photon pair [1, 2] for realizing quantum computation and quantum information. Superconducting devices have an advantage to obtain robustly coherent quantum states because of its coherent nature [3, 4, 5]. Superconducting LEDs [6] have been originally proposed in the context of superradiation. They are, however, a promising candidate to create an entangled photon pair [7]. A recent theoretical study predicts the Josephson radiation in a superconducting pn junction [9]. Thus superconductor/semiconductor LED hybrids undoubtedly have a possibility to produce technologies in the next generation.

The radiative recombination of Cooper pairs has been observed recently in a InGaAs/InP pn junction attaching onto a superconductor Nb [8]. The electroluminescence becomes drastically large at low temperatures below the superconducting transition temperature T_c of Nb electrode. Surprisingly degree of the enhancement in the luminescence intensity is one order of magnitude. Although the effects of superconductivity on the radiative recombination are clear in experiments, a mechanism has been an open problem. We theoretically address this issue in this paper. We study the emission spectra of photon in a superconducting pn junction based on the second order perturbation theory. In the second order expansion, we find that a peculiar recombination process to superconductivity enlarges the luminescence intensity, where two electrons recombine with two p-type carriers as a Cooper. The theoretical results explain characteristic features of the experimental findings [8]. This paper not only figures out a mechanism of the large amplitude of luminescence intensity but also gives a guide for designing highly functional superconducting light-emitting devices.

Let us consider a p-type semiconductor / superconductor junction as shown in Fig. 1(a). The energy is

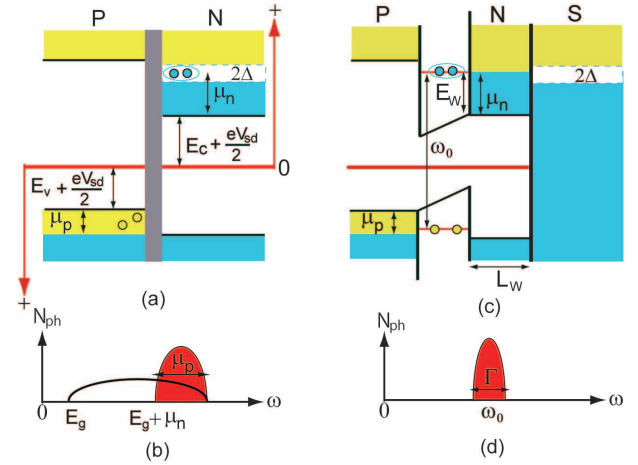


FIG. 1: (Color online) Schematic energy diagram of pn junctions. A theoretical model used for calculation is shown in (a). In (c), a real junction in an experiment is illustrated. Theoretical results of the photon spectra are shown in (b) and (d).

measured from the horizontal line indicated by '0'. The sign of energy in a p-type semiconductor is chosen to be opposite to that in a superconductor. We assume that a semiconductor and a superconductor are in their local equilibrium which are characterized by the local chemical potential μ_p and μ_n , respectively. The edges of the conduction and valence bands are E_c and E_v , respectively. In what follows, we use a unit of $\hbar = k_B = c = 1$, where k_B is the Boltzmann constant and c is the speed of light. The p-type semiconductor is described by

$$H_p = \sum_{\mathbf{k}, \sigma} \epsilon_p(\mathbf{k}) b_{\mathbf{k}, \sigma}^\dagger b_{\mathbf{k}, \sigma}, \quad (1)$$

where $\epsilon_p(\mathbf{k}) = k^2/(2m_p) + E_v + eV_{sd}/2$, m_p is the effective mass, V_{sd} is the applied bias voltage across the junction,

and $b_{\mathbf{k},\sigma}^\dagger(b_{\mathbf{k},\sigma})$ is the creation (annihilation) operator of a p-type carrier with a wave number $\mathbf{k}$ and spin $\sigma = \uparrow$ or $\downarrow$. The photon states is described by

$$H_{ph} = \sum_{\mathbf{q}} \omega_{\mathbf{q}} \left(a_{\mathbf{q}}^\dagger a_{\mathbf{q}} + \frac{1}{2} \right), \quad (2)$$

where $a_{\mathbf{q}}^\dagger(a_{\mathbf{q}})$ is the creation (annihilation) operator of a photon with a wave number $\mathbf{q}$ and an energy $\omega_{\mathbf{q}}$. The normal state in a metal is described by

$$H_{nn} = \sum_{\mathbf{k},\sigma} \left(\frac{k^2}{2m_n} + E_c + \frac{eV_{sd}}{2} \right) c_{\mathbf{k},\sigma}^\dagger c_{\mathbf{k},\sigma}, \quad (3)$$

with m_n being the effective mass. The electron-photon interaction Hamiltonian reads

$$H_I = \sum_{\mathbf{k},\mathbf{q},\sigma} B_{\mathbf{k},\mathbf{q}} b_{\mathbf{k}-\mathbf{q},\sigma} c_{\mathbf{k},\sigma} a_{\mathbf{q}}^\dagger + \text{H.c.}, \quad (4)$$

where $B_{\mathbf{k},\mathbf{q}}$ is the coupling energy. On the basis of the second order perturbation theory, the number of photon $N_{ph} = \sum_{\mathbf{q}} a_{\mathbf{q}}^\dagger a_{\mathbf{q}}$ is calculated as

$$\langle N_{ph} \rangle = \langle N_{ph}(1) \rangle + \langle N_{ph}(2) \rangle, \quad (5)$$

$$\langle N_{ph}(1) \rangle = \int_{-\infty}^t dt_1 \int_{-\infty}^t dt_2 \langle \chi_0 | H_I(t_1) N_{ph} H_I(t_2) | \chi_0 \rangle, \quad (6)$$

$$\langle N_{ph}(2) \rangle = \int_{-\infty}^{t_2} dt_1 \int_{-\infty}^t dt_2 \int_{-\infty}^{t_3} dt_3 \int_{-\infty}^{t_4} I(2), \quad (7)$$

$$I(2) = \langle \chi_0 | H_I(t_1) H_I(t_2) N_{ph} H_I(t_3) H_I(t_4) | \chi_0 \rangle, \quad (8)$$

$$| \chi_0 \rangle \rightarrow | 0 \rangle \otimes | N \rangle \otimes | P \rangle, \quad (9)$$

where $| 0 \rangle$ is the zero photon state.

The BCS theory describes superconducting states,

$$H_{ns} = \sum_{\mathbf{k},\sigma} E_k \gamma_{\mathbf{k},\sigma}^\dagger \gamma_{\mathbf{k},\sigma}, \quad (10)$$

where $E_k = \sqrt{\xi_n^2(k) + \Delta^2}$, $\xi_n(k) = k^2/2m_n - \mu_n$, Δ is the pair potential, and $\gamma_{\mathbf{k},\sigma}^\dagger(\gamma_{\mathbf{k},\sigma})$ is the creation (annihilation) operator of Bogoliubov quasiparticle. This description, however, is valid within a small energy scale near the Fermi level which is at $\tilde{\mu}_n = E_c + eV_{sd}/2 + \mu_n$ measured from '0'. To apply the BCS theory to the present issue, a rule is necessary to describe the operator in the interaction picture. The canonical transformation connects an electron operator and Bogoliubov operators by

$$c_{\mathbf{k},\sigma}^\dagger(t) = e^{i\tilde{\mu}_n t} \left(u_k e^{iE_k t} \gamma_{\mathbf{k},\sigma}^\dagger - s_\sigma v_k e^{-iE_k t} \gamma_{-\mathbf{k},\bar{\sigma}} \right), \quad (11)$$

in $\langle \chi_0 | \cdots | \chi_0 \rangle$, where $u_k(v_k) = [(1 + (-)\xi_n(k)/E_k)/2]^{1/2}$, $s_\sigma = 1(-1)$ for $\sigma = \uparrow(\downarrow)$, and $\bar{\sigma}$ means the opposite spin to σ . The thermal average of operators is carried out in the local equilibrium. In a p-type semiconductor, for instance, the average of operators are calculated in

$$H'_p = \sum_{\mathbf{k},\sigma} \xi_p(k) b_{\mathbf{k},\sigma}^\dagger b_{\mathbf{k},\sigma}, \quad (12)$$

instead of Eq. (1) with $\xi_p(k) = k^2/2m_p - \mu_p$. In a superconductor, the average of the Bogoliubov operators are calculated in Eq. (10). In Eq. (9), $| P \rangle$ means the state vector of p-type carrier in the local equilibrium and $| N \rangle$ indicates the BCS state in the local equilibrium.

The time average of the photon number $\overline{\langle N_{ph} \rangle}$ corresponds to the luminescence intensity and it in the first order perturbation expansion results in

$$\overline{\langle N_{ph}(1) \rangle} = 2\pi \sum_{\mathbf{k},\mathbf{q},\sigma} |B_{\mathbf{k},\mathbf{q}}|^2 f_{\mathbf{k}-\mathbf{q}}^p \times [u_k^2 f_k^n \delta(\tilde{\omega} - E_k) + v_k^2 (1 - f_k^n) \delta(\tilde{\omega} + E_k)], \quad (13)$$

where $\tilde{\omega} = \omega_{\mathbf{q}} - E_g - \mu_n - \mu_p - \xi_p(\mathbf{k} - \mathbf{q})$, $E_g = E_v + E_c + eV_{sd}$, $f_k^n = [1 - \tanh(E_k/2T)]/2$, and $f_k^p = [1 - \tanh(\xi_p(k)/2T)]/2$. This result recovers the photon spectra in a normal pn junction by tuning $\Delta \rightarrow 0$, which means that $E_k \rightarrow -\xi_n(k)$, $u_k \rightarrow 0$, $v_k \rightarrow 1$ for $k < k_F$ and $E_k \rightarrow \xi_n(k)$, $u_k \rightarrow 1$, $v_k \rightarrow 0$ for $k > k_F$ with k_F being the Fermi wave number satisfying $k_F^2/2m_n = \mu_n$. The threshold of spectra is E_g and the width of spectra is given by $\mu_n + \mu_p$. The spectra in Eq. (13) have a broad profile reflecting the quasiparticle density of states as shown in Fig. 1(b).

One of the characteristics peculiar to superconductivity is a giant oscillator strength [6]. This comes from the much freedom of the wave vector $\mathbf{k}$ for the remaining elementary excitation when a Cooper pair decays radiatively with a p-type carrier with the opposite wave vector $-\mathbf{k}$. This would gives the large luminescence intensity in the experiment [8]. This effect of the giant oscillator strength works also in the first stage in the second order expansion while not in the second process. The other characteristics is coming from the resonant enhancement due to the nearly degenerate nature of the final and intermediate states close to the initial state. This is shown in the following calculation.

The results of the second order perturbation are given by

$$I(2) = \sum_{\mathbf{k}_1 \cdots \mathbf{k}_4, \mathbf{q}_1 \cdots \mathbf{q}_4, \sigma_1 \cdots \sigma_4} e^{-i\Omega_1 t_1 - i\Omega_2 t_2 + i\Omega_3 t_3 + i\Omega_4 t_4} \times B_{\mathbf{k}_1, \mathbf{q}_1}^* B_{\mathbf{k}_2, \mathbf{q}_2}^* B_{\mathbf{k}_3, \mathbf{q}_3} B_{\mathbf{k}_4, \mathbf{q}_4} Q_{Ph} Q_P Q_N, \quad (14)$$

with $\Omega_j(\mathbf{k}_j, \mathbf{q}_j) = \omega_{\mathbf{q}_j} - \epsilon_P(\mathbf{k}_j - \mathbf{q}_j) - \tilde{\mu}_n$. The average of the operators Q_{Ph} , Q_P and Q_N are calculated as follows,

$$Q_{Ph} = \sum_{\mathbf{q}_5} \langle 0 | a_{\mathbf{q}_1} a_{\mathbf{q}_2} a_{\mathbf{q}_5}^\dagger a_{\mathbf{q}_5} a_{\mathbf{q}_3}^\dagger a_{\mathbf{q}_4}^\dagger | 0 \rangle, \\ = 2(\delta_{14}^{\mathbf{q}} \delta_{23}^{\mathbf{q}} + \delta_{13}^{\mathbf{q}} \delta_{24}^{\mathbf{q}}), \quad (15)$$

$$Q_P = \langle P | b_{\mathbf{p}_1, \sigma_1}^\dagger b_{\mathbf{p}_2, \sigma_2}^\dagger b_{\mathbf{p}_3, \sigma_3} b_{\mathbf{p}_4, \sigma_4} | P \rangle, \\ = f_{\mathbf{p}_1}^p f_{\mathbf{p}_2}^p (\delta_{14}^{\sigma} \delta_{23}^{\sigma} \delta_{14}^{\mathbf{p}} \delta_{23}^{\mathbf{p}} - \delta_{13}^{\sigma} \delta_{24}^{\sigma} \delta_{13}^{\mathbf{p}} \delta_{24}^{\mathbf{p}}), \quad (16)$$

where $\delta_{ij}^{\mathbf{q}} = \delta_{\mathbf{q}_i, \mathbf{q}_j}$, $\delta_{ij}^{\sigma} = \delta_{\sigma_i, \sigma_j}$, $\delta_{ij}^{\mathbf{p}} = \delta_{\mathbf{p}_i, \mathbf{p}_j}$ and $\mathbf{p}_j = \mathbf{k}_j - \mathbf{q}_j$. By applying the Bogoliubov transformation, we

find,

$$\begin{aligned}
Q_N = & \langle N | (u_{k_1} e^{iE_{k_1} t_1} \gamma_{\mathbf{k}_1, \sigma_1}^\dagger - \sigma_1 v_{k_1} e^{-iE_{k_1} t_1} \gamma_{-\mathbf{k}_1, \bar{\sigma}_1}) \\
& \times (u_{k_2} e^{iE_{k_2} t_2} \gamma_{\mathbf{k}_2, \sigma_2}^\dagger - \sigma_2 v_{k_2} e^{-iE_{k_2} t_2} \gamma_{-\mathbf{k}_2, \bar{\sigma}_2}) \\
& \times (u_{k_3} e^{-iE_{k_3} t_3} \gamma_{\mathbf{k}_3, \sigma_3} - \sigma_3 v_{k_3} e^{iE_{k_3} t_3} \gamma_{-\mathbf{k}_3, \bar{\sigma}_3}^\dagger) \\
& \times (u_{k_4} e^{-iE_{k_4} t_4} \gamma_{\mathbf{k}_4, \sigma_4} - \sigma_4 v_{k_4} e^{iE_{k_4} t_4} \gamma_{-\mathbf{k}_4, \bar{\sigma}_4}^\dagger) | N \rangle, \quad (17)
\end{aligned}$$

which gives twelve terms. In what follows, we extract the most dominant contribution in the second order terms. The average of Q_N includes following four terms

$$\begin{aligned}
Q_N(S) = & u_{k_1} v_{k_1} u_{k_3} v_{k_3} \delta_{\sigma_1, \bar{\sigma}_2} \delta_{\sigma_3, \bar{\sigma}_4} \delta_{\mathbf{k}_1, -\mathbf{k}_2} \delta_{\mathbf{k}_3, -\mathbf{k}_4} \sigma_1 \sigma_3 \\
& \times \left[e^{iE_{k_1}(t_1-t_2)} e^{-iE_{k_3}(t_3-t_4)} f_{k_1}^n (1 - f_{k_3}^n) \right. \\
& + e^{-iE_{k_1}(t_1-t_2)} e^{iE_{k_3}(t_3-t_4)} f_{k_3}^n (1 - f_{k_1}^n) \\
& - e^{-iE_{k_1}(t_1-t_2)} e^{-iE_{k_3}(t_3-t_4)} (1 - f_{k_1}^n) (1 - f_{k_3}^n) \\
& \left. - e^{iE_{k_1}(t_1-t_2)} e^{iE_{k_3}(t_3-t_4)} f_{k_1}^n f_{k_3}^n \right]. \quad (18)
\end{aligned}$$

Because $\delta_{\sigma_3, \bar{\sigma}_4} \delta_{\mathbf{k}_3, -\mathbf{k}_4}$ in Eq. (18) means the destruction of two electrons as a Cooper pair, $Q_N(S)$ describe effects of superconductivity on the emission spectra. Another eight terms in Q_N contribute to the emitting processes described by Fig. 2(b) which gives the luminescence intensity proportional to $\langle N_{ph}(1) \rangle^2$. We will show that $Q_N(S)$ gives a large contribution to the emission spectra at $\delta \mathbf{q} = \mathbf{q}_1 + \mathbf{q}_2 = 0$, ($\delta \mathbf{q} = \mathbf{q}_3 + \mathbf{q}_4 = 0$ in other wards) [10]. Substituting Eqs. (15), (16) and (18) into Eq. (14) and carrying out time integrations, we obtain

$$\langle N_{ph}(2) \rangle = 4\pi |B|^4 \sum_{\mathbf{q}, \sigma} \delta(\Omega_{\mathbf{k}_F, \mathbf{q}}) I_0, \quad (19)$$

$$\begin{aligned}
I_0 = & \sum_{\mathbf{k}} \left[\frac{f_{\mathbf{k}}^n (1 - f_{\mathbf{k}}^n)}{(E_{\mathbf{k}} - i/\tau)^2} + \frac{f_{\mathbf{k}}^n (1 - f_{\mathbf{k}}^n)}{(E_{\mathbf{k}} + i/\tau)^2} \right. \\
& \left. + \frac{(f_{\mathbf{k}}^n)^2 + (1 - f_{\mathbf{k}}^n)^2}{E_{\mathbf{k}}^2 + (1/\tau)^2} \right] \frac{\Delta^2}{E_{\mathbf{k}}^2}, \quad (20)
\end{aligned}$$

where we introduce a relaxation time τ to remove effects of the perturbation at $t \rightarrow -\infty$, we neglect dependence of B on wave numbers and assume $f_{\mathbf{k}_F - \mathbf{q}}^p = 1$. At $1/\tau = 0$, $I_0 = \pi N_0 / 2\Delta$ essentially diverges for small Δ with N_0 denoting the normal density of states in a superconductor at the Fermi energy. The singular behavior at small Δ in Eq. (20) is a sign of the large luminescence intensity due to superconductivity.

We first show mathematical reasons of the singularity. Then we will discuss the physics behind the phenomenon. A two-photon emitting process in $Q_N(S)$ is illustrated in Fig. 2(a). The annihilation of a Cooper pair is described by $c_{-\mathbf{k}, \downarrow} c_{\mathbf{k}, \uparrow}$ which includes a operator $\gamma_{\mathbf{k}, \uparrow}^\dagger \gamma_{\mathbf{k}, \uparrow}$. Let us assume that the energy of the initial state is zero. In the first order expansion, the operation of $\gamma_{\mathbf{k}, \uparrow}$ to the BSC state decreases energy by $E_{\mathbf{k}} + \tilde{\mu}_n$. At the same time, a p-type carrier with energy $\epsilon_p(\mathbf{k} - \mathbf{q})$ is destructed and a photon with energy ω_q

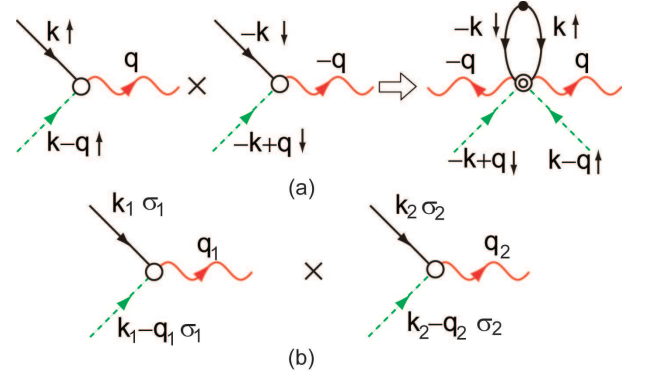


FIG. 2: (Color online) Recombination processes in the second order perturbation expansion, where solid, broken and wavy lines represent the propagation of an electron, a p-type carrier and a photon, respectively. In (a), a recombination of a Cooper pair in $Q_N(S)$ is shown. In (b), a recombination process other than $Q_N(S)$ is illustrated.

is created. Thus the energy of the intermediate state δE_1 results in $\delta E_1 = \omega_q - \epsilon_p(\mathbf{k} - \mathbf{q}) - E_{\mathbf{k}} - \tilde{\mu}_n = \Omega_{\mathbf{k}, \mathbf{q}} - E_{\mathbf{k}}$ which is the energy denominator in the perturbation expansion. In the second order, the operation of $\gamma_{\mathbf{k}, \uparrow}^\dagger$, the destruction of a p-type carrier, and the creation of a photon gain energy by $E_{\mathbf{k}} - \tilde{\mu}_n$, $-\epsilon_p(-\mathbf{k} + \mathbf{q})$, and ω_{-q} , respectively. Therefore the difference in energy between the intermediate state and the final one becomes $\delta E_2 = \omega_q - \epsilon_p(\mathbf{k} - \mathbf{q}) + E_{\mathbf{k}} - \tilde{\mu}_n = \Omega_{\mathbf{k}, \mathbf{q}} + E_{\mathbf{k}}$. The perturbation theory requires the energy conservation between the initial and the final states, (i.e., $\delta E_1 + \delta E_2 = 0$), which leads to $2\Omega_{\mathbf{k}, \mathbf{q}} = 0$. As a result, only a small value of $E_{\mathbf{k}}$ remains in the denominator as shown in Eq. (20). The physics behind the phenomena is simple. The BCS state can have ability to emit a pair of photons with remaining its state almost unchanged because the BCS state is the eigen state of $\gamma_{\mathbf{k}, \uparrow}^\dagger \gamma_{\mathbf{k}, \uparrow}$. The equation $\Omega_{\mathbf{k}_F, \mathbf{q}} = 0$ is the condition for emitting a photon. The threshold and width of spectra are $E_g + \mu_n$ and μ_p , respectively. In Fig. 1(b), we show predicted spectra in the second order process.

The singular behavior in perturbation expansion implies an importance of higher order terms to predict the luminescence intensity quantitatively. Here we do not discuss this issue, but choose an alternative way of regularizing the obtained results for qualitative argument. In what follows, we introduce a finite relaxation time. First we consider mean free time due to elastic impurity scatterings τ_0 . At $T = 0$, we obtain $I_0 = I_{00}(0) 2\alpha^2 / (\sqrt{1 + \alpha^2} (\alpha + \sqrt{1 + \alpha^2}))$, where $\alpha = \tau_0 \Delta_0$, Δ_0 is the pair potential at the zero temperature and $I_{00}(0) = \pi N_0 / 2\Delta_0$ is Eq. (20) at $T = 0$. At $T \lesssim T_c$, we find

$$\frac{I_0}{I_{00}(0)} \approx \begin{cases} c_0 \alpha^2 (\Delta / \Delta_0)^2 \Delta_0 / T & \alpha \lesssim 1 \\ \alpha^3 (\Delta / \Delta_0)^2 & \alpha \gg 1, \end{cases} \quad (21)$$

where c_0 is a constant of the order of unity. In Fig. 3(a), we show I_0 as a function of temperature for several choices of α , where we describe the dependence of Δ on temperature by the BCS theory. The amplitude of I_0 at $T = 0$ is suppressed in the dirty limit as shown in a result with $\alpha = 0.2$. The amplitude at $T = 0$ increases with increasing α . At $\alpha = 1$, $I_0(0)$ has almost the same amplitude as $I_{00}(0)$. When we increase α up to 2.0, the results show a bump just below T_c . Next we consider inelastic scatterings described by $1/\tau_{ie} = C_{ie}(T/T_c)^p$, where C_{ie} is a coupling constant and p depends on scattering sources such as $p = 1$ for electron-phonon scatterings and $p = 2$ for repulsive electron-electron interaction. In Fig. 3(b), we calculate I_0 for several choices of C_{ie} and p . Since $1/\tau_{ie} \rightarrow 0$ at $T = 0$, the amplitude is close to $I_{00}(0)$ at $T = 0$. When we decrease C_{ie} , the bump appears below T_c as well as in (a). For $1/\tau \lesssim \Delta_0$, the luminescence intensity at $T \lesssim T_c$ is then given by

$$\overline{\langle N_{ph}(2) \rangle} \approx 4\pi c_0 |B|^4 N_0 \frac{(\tau \Delta)^2}{T} \sum_q \delta(\Omega_{k_F, q}). \quad (22)$$

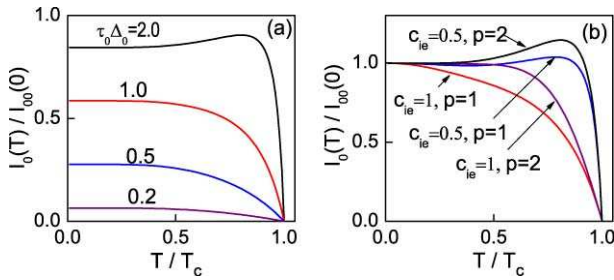


FIG. 3: Temperature dependence of luminescence intensity. In (a), we consider relaxation time due to the elastic impurity scatterings by $\alpha = \tau_0 \Delta_0$. In (b), we consider the relaxation due to inelastic scatterings.

Finally we modify Eq. (22) to describe the photon spectra in the experiment [8] as shown in Fig. 1(c). In the real junction, a superconductor is attached to a n-type semiconductor whose thickness is L_w . The proximity effect enhances the luminescence intensity. In Eq. (22), Δ is proportional to the amplitude of a Cooper pair. In n-type semiconductor, the proximity effect enables the pair amplitude which proportional to $\Delta e^{-L_w/\xi_T}$ with $\xi_T = \sqrt{D/2\pi T}$ and D being the diffusion constant in the n-type semiconductor. The photon pairs are emitted in a quantum well between the p- and n-type semiconductors. The level in the quantum well E_w should coincide with the Fermi level in the n-type semiconductor μ_n . Namely $|E_w - \mu_n|$ must be less than both the Thouless energy $E_{Th} = D/L_w^2$ and Δ . This resonant condition is particularly important for a Cooper pair to penetrate into the

quantum well. The emission spectra has a peak at ω_0 and the peak width is given by $\Gamma = t_w^2 N_0$, where t_w is the transfer integral between the quantum well and the semiconductor. The argument above is summarized by an equation for $T \lesssim T_c$

$$\overline{\langle N_{ph}(2) \rangle} \approx |B|^4 N_0 \Gamma \sum_{q, \sigma} \frac{\Delta^2 \tau^2 e^{-2L_w/\xi_T/T}}{(\omega_q - \omega_0)^2 + (\Gamma)^2}, \quad (23)$$

where we introduce the Lorentz resonant function by hand. In the experiment, ξ_T is estimated to be much larger than L_w below T_c . Thus the theoretical results in Fig. 3 can describe experimental results of the luminescence intensity. In fact, the experimental results of Fig. 6(b) in Ref. 8 show a very similar line shape to that in Fig. 3(a) with $\alpha = 1$.

In conclusion, we have studied the photon emission spectra in a superconducting pn junction based on the second order perturbation theory for electron-photon interaction. We have found in the second order expansion that a peculiar recombination process to superconductivity enlarges the luminescence intensity. The theoretical results explain temperature dependence of the luminescence intensity observed in an recent experiment.

-
- [1] P. Michler, A. Kiraz, C. Becher, W. V. Schoenfeld, P. M. Petroff, Lidong Zhang, E. Hu, A. Imamogulu, Science **290**, 2282 (2000).
 - [2] O. Benson, C. Santori, M. Pelton, and Y. Yamamoto, Phys. Rev. Lett. **84**, 2513 (2000).
 - [3] I. Chiorescu, P. Bertet, K. Semba, Y. Nakamura, C. J. P. M. Harmans, and J. E. Mooij, Nature **431**, 159 (2004).
 - [4] A. Wallraff, D. I. Schuster, A. Blais, L. Frunzio, R.-S. Huang, J. Majer, S. Kumar, S. M. Girvin, and R. J. Schoelkopf, Nature **431**, 162 (2004).
 - [5] N. Katz, M. Ansmann, R. C. Bialczak, E. Lucero, R. McDermott, M. Neeley, M. Steffen, E. M. Weig, A. N. Cleland, J. M. Martinis, and A. N. Korotkov, Science **312**, 1498 (2006).
 - [6] E. Hanamura, physica stat. solidi b **234**, 166 (2002).
 - [7] I. Suemune, T. Akazaki, K. Tanaka, M. Jo, K. Uesugi, M. Endo, H. Kumano, E. Hanamura, H. Takayanagi, M. Yamanishi, and H. Kan, Japan. J. Appl. Phys. **45**, 9264 (2006).
 - [8] Y. Hayashi, K. Tanaka, T. Akazaki, M. Jo, H. Kumano, and I. Suemune, Appl. Phys. Express **1**, 011701 (2008).
 - [9] P. Recher, Y. V. Nazarov, L. Kouwenhoven, arXiv:0902-4468.
 - [10] The speed of light is much larger than the Fermi velocity. In such case, this condition becomes $|\mathbf{q}_1| \sim |\mathbf{q}_2|$.